

Heat transport in $\text{SrCu}_2(\text{BO}_3)_2$ and CuGeO_3

M. Hofmann^a T. Lorenz^a A. Freimuth^a G.S. Uhrig^b
H. Kageyama^c Y. Ueda^c G. Dhalenne^d A. Revcolevschi^d

^a*II. Phys. Institut, Universität zu Köln, Zùlpicher Str. 77, 50937 Köln, Germany*

^b*Inst. für Theoretische Physik, Univ. zu Köln, Zùlpicher Str. 77, 50937 Köln*

^c*Inst. for Sol. State Phys., Univ. of Tokyo, Kashiwanoha 5-1-5, Kashiwa, Japan*

^d*Lab. de Physico-Chimie des Solides, Univ. Paris-Sud, 91405 Orsay, France*

Abstract

In the low dimensional spin systems $\text{SrCu}_2(\text{BO}_3)_2$ and CuGeO_3 the thermal conductivities along different crystal directions show pronounced double-peak structures and strongly depend on magnetic fields. For $\text{SrCu}_2(\text{BO}_3)_2$ the experimental data can be described by a purely phononic heat current and resonant scattering of phonons by magnetic excitations. A similar effect seems to be important in CuGeO_3 , too but, in addition, a magnetic contribution to the heat transport may be present.

Key words:

Heat transport, low dimensional quantum spin systems

One topic of interest in low dimensional (D) quantum spin systems is the dynamics of magnetic excitations, which e.g. are expected to move without dissipation in an $S=1/2$ Heisenberg chain [1]. This may lead to an unusual thermal conductivity in real, (quasi-)low-D systems. Experimental evidence for a large magnetic contribution κ^{mag} to the heat transport has been found in $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ containing both, spin chains and ladders [2]. Here, κ shows an enormous maximum around 200 K which is present *only* for heat transport parallel to the ladder (and chain) direction. This has been interpreted as a huge magnetic contribution to κ , which adds to a phononic contribution κ^{ph} giving rise to low-T maxima around 20 K for all three crystal directions. In this paper we present a study of the anisotropic heat transport in the spin Peierls (SP) system CuGeO_3 and in the 2D dimer spin system $\text{SrCu}_2(\text{BO}_3)_2$ [3], whose magnetic planes represent a realization of the Shastry Sutherland model [4].

The thermal conductivities of tetragonal $\text{SrCu}_2(\text{BO}_3)_2$ parallel (κ_c) and perpendicular (κ_a) to the magnetic planes show pronounced double peaks with a

first maximum around 4 K for both directions and a second one around 60 K and 30 K for κ_a and κ_c , respectively (see Fig. 1). In a magnetic field the maxima at low T are suppressed whereas those at high T remain unchanged. At first glance, one might suspect that the field-dependent double peaks result from the superposition of a phononic and a magnetic contribution. However, the similar behavior of κ_a and κ_c makes any explanation depending on a κ^{mag} very unlikely, since κ^{mag} perpendicular to the magnetic planes should be negligible. Moreover, the triplet excitations of $\text{SrCu}_2(\text{BO}_3)_2$ are almost dispersionless along the magnetic planes [3], so that even within the planes κ^{mag} is expected to be very small. This led us to a model that is based on a purely phononic heat current and explains the field-dependent double peaks by resonant scattering of phonons by magnetic excitations. It can be visualized as (i) the absorption of a phonon of energy ω by exciting a (magnetic) two-level system and (ii) its subsequent de-excitation by emitting another phonon of same energy but different momentum (for more details see [5]). Such a scattering is most active in a certain temperature range depending on the energy splitting of the two-level system. Spin conservation requires a thermally excited triplet and the phonon excites a second triplet which combines with the first one to total spin $S_{tot} = 1$. Thus, the scattering rate depends on the thermal population of excited triplets. It also depends on the magnetic field due to the Zeeman splitting. Within this model our experimental data for zero field can be fitted very well. Since these fits fix all parameters the data for higher fields are calculated from the Zeeman splitting without further parameter adjustment. As shown by the solid lines in Fig. 1 our model describes the general features of κ_a and κ_c very well; κ_c is even quantitatively reproduced up to 17 T, whereas the field dependence of κ_a is slightly overestimated.

The thermal conductivities along the a , b , and c axis of orthorhombic CuGeO_3 are shown in Fig. 2. Our results confirm those previously measured for κ_c ($\parallel$ to the spin chains) [6] showing one maximum below and a second one above the SP transition at $T_{\text{SP}} \sim 14$ K. With increasing field the low T maximum is continuously suppressed up to 14 T and then slightly increases again. This non-monotonic field dependence is related to the occurrence of the so called incommensurate phase above ~ 12.5 T [7]. Although the data of CuGeO_3 qualitatively resemble those of $\text{SrCu}_2(\text{BO}_3)_2$ the situation in the two compounds is rather different. A sizeable κ^{mag} — though not necessary for an explanation of a field-dependent double peak — may be present in CuGeO_3 since the triplet excitations have considerable dispersion [10]. In addition, there is the SP transition. Above T_{SP} the energy gap closes and strong structural fluctuations are observed up to ~ 35 K [8]. All these effects may influence κ^{ph} and/or κ^{mag} making a reliable description of κ difficult.

In order to clarify whether a magnetic contribution to κ_c is present in CuGeO_3 we have also measured κ_b and κ_a ($\perp$ to the spin chains). As shown in Fig. 2 κ_b behaves very similar to κ_c apart from the absolute value which is a factor of

~ 3 smaller for κ_b than for κ_c . An anisotropy ratio of ~ 3 is present between the sound velocities along c and b ($v_c \sim 7600$ m/s and $v_b \sim 2400$ m/s [9]), but also for the triplet dispersions along c and b [10]. Therefore, one can neither exclude nor confirm the presence of a sizeable magnetic contribution to the heat current from this anisotropy. Finally, we consider the a axis. The sound velocity amounts to $v_a \sim 3600$ m/s [9] whereas the magnetic dispersion is essentially zero [10], i.e. κ_a^{mag} is negligible. At 300 K the anisotropy between κ_c , κ_b and (the purely phononic) κ_a reflects that of the v_i ($i = a, b, c$). Therefore κ_c^{mag} and κ_b^{mag} can also be neglected at room temperature. This is not surprising because the magnetic coupling constants in CuGeO_3 are much smaller; $J_c \sim 120 - 180$ K and $J_b \sim 0.1J_c$ depending on the model [10,11]. Unfortunately, κ_a cannot help to separate κ^{ph} and κ^{mag} along b and c at low T because the layered structure of CuGeO_3 along a limits the mean free path by so-called sheet-like faults. This prevents a strong increase of κ_a at low T and already explains the completely different behavior of κ_a compared to κ_b and κ_c , regardless their field dependent double-peaks.

In conclusion, the thermal conductivities of CuGeO_3 and $\text{SrCu}_2(\text{BO}_3)_2$ show pronounced, magnetic-field dependent double-peaks. For $\text{SrCu}_2(\text{BO}_3)_2$ this arises from resonant scattering of a phononic heat current by magnetic excitations. In CuGeO_3 a similar effect seems to play a role but further studies are necessary in order to clarify the dynamics of the magnetic excitations.

References

- [1] X. Zotos *et al.*, Phys. Rev. B **55**, 11029 (1997).
- [2] A. V. Sologubenko *et al.*, Phys. Rev. Lett. **84**, 2714 (2000).
- [3] H. Kageyama *et al.*, Phys. Rev. Lett. **84**, 5876 (2000).
- [4] B. S. Shastry and B. Sutherland, Physica B **108**, 1069 (1981).
- [5] M. Hofmann *et al.*, Phys. Rev. Lett. **87**, 047202 (2001).
- [6] Y. Ando *et al.*, Phys. Rev. B **58**, R2913 (1998).
- [7] T. Lorenz *et al.*, Phys. Rev. Lett. **81**, 148 (1998).
- [8] J.P. Schoeffel *et al.*, Phys. Rev. B **53**, 14971 (1996).
- [9] M. Saint-Paul *et al.*, Phys. Rev. B **52**, 15298 (1995).
- [10] M. Nishi *et al.*, Phys. Rev. B **50**, 6508 (1994).
- [11] K. Fabricius *et al.*, Phys. Rev. B **57**, 1102 (1998).

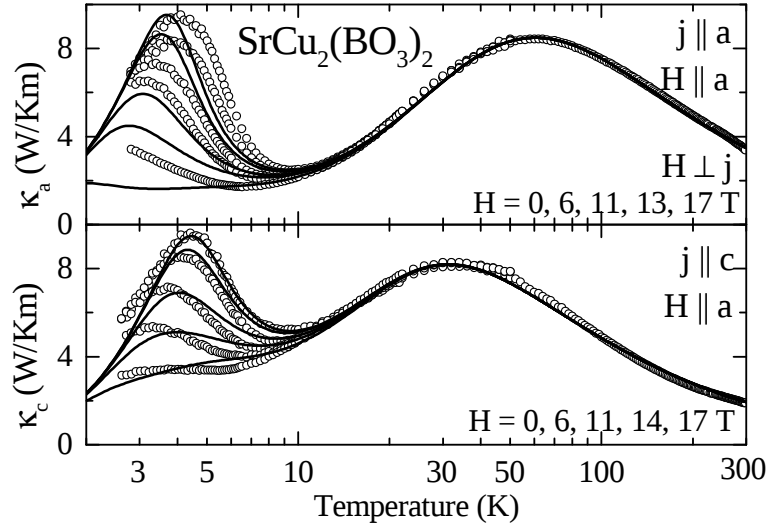


Fig. 1. Thermal conductivity κ_a (top) and κ_c (bottom) of tetragonal $\text{SrCu}_2(\text{BO}_3)_2$ on a logarithmic temperature scale for various fields. On increasing field the low- T maximum is suppressed. Lines are theoretical curves calculated for the same fields.

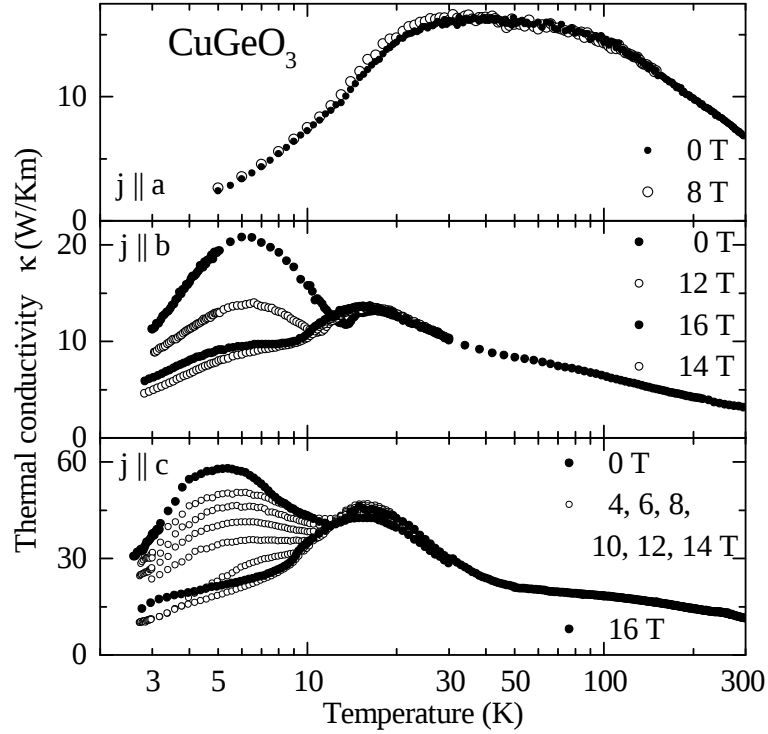


Fig. 2. Thermal conductivity κ_a , κ_b and κ_c (from top to bottom) of orthorhombic CuGeO_3 on a logarithmic temperature scale for various fields. κ_a is field-independent whereas κ_b and κ_c decrease with increasing field up to 14 T and then increase again.